



PRODUCT/PROCESS CHANGE NOTIFICATION

PCN IPG-IPC/14/8322
Dated 10 Feb 2014

**Qualification of a new HD lead frame and new resin
SUMITOMO G630AY for SO 8 package in ST Bouskoura (Morocco)**

Table 1. Change Implementation Schedule


Forecasted implementation date for change	01-Mar-2014
Forecasted availability date of samples for customer	01-Mar-2014
Forecasted date for STMicroelectronics change Qualification Plan results availability	03-Feb-2014
Estimated date of changed product first shipment	12-May-2014

Table 2. Change Identification

Product Identification (Product Family/Commercial Product)	See attached
Type of change	Package assembly material change
Reason for change	Capacity increase
Description of the change	Introduction of a new HD lead frame and new resin SIMITOMO G630AY for the assembly of products housed in SO 08 package, in ST Bouskoura (Morocco).
Change Product Identification	By date code and relevant traceability
Manufacturing Location(s)	

Table 3. List of Attachments

Customer Part numbers list	
Qualification Plan results	



Customer Acknowledgement of Receipt		PCN IPG-IPC/14/8322	
Please sign and return to STMicroelectronics Sales Office		Dated 10 Feb 2014	
<input type="checkbox"/> Qualification Plan Denied	Name:		
<input type="checkbox"/> Qualification Plan Approved	Title:		
	Company:		
<input type="checkbox"/> Change Denied	Date:		
<input type="checkbox"/> Change Approved	Signature:		
Remark			
.....			
.....			
.....			
.....			
.....			
.....			
.....			
.....			
.....			
.....			

DOCUMENT APPROVAL

Name	Function
Sandrini, Francesca Marta	Marketing Manager
Vavassori, Emanuele	Marketing Manager
Sandrini, Francesca Marta	Product Manager
Vavassori, Emanuele	Product Manager
Moretti, Paolo	Q.A. Manager
Motta, Antonino	Q.A. Manager



WHAT:

We have qualified a new HD lead frame for the assembly of products housed in SO 08 package in ST Bouskoura (Morocco). In addition we have introduced a new halogen free resin SUMITOMO G630AY to replace the current SUMITOMO G700K.

WHY:

To rationalize manufacturing and to increase our production capacity.

HOW:

As per the attached Reliability Qualification plan, we have evaluated and qualified the a.m. new material through trials performed on 3 test vehicles (UE27BD6, 0303AC6 and U093ADZ).

WHEN:

The new HD lead frame and resin will be implemented from March, 2014.

Samples of the a.m. test vehicles are available. For all the other involved products, they can be provided on request, in 4 weeks A.R.O.

Reliability Report

Qualification of new HD LF and new resin SUMITOMO G630AY for SO8 package in BOUSKOURA

General Information	
Product Line	<i>UE27</i>
Product division	<i>I&PC</i>
Package	<i>SO8</i>
Silicon process technology	<i>BCD2S</i>

Locations	
Wafer fab location	<i>ANG MO KIO 6"</i>
Assembly plant location	<i>BOUSKOURA (Morocco)</i>
Reliability assessment	<i>Pass</i>

General Information	
Product Line	<i>0303</i>
Product division	<i>I&PC</i>
Package	<i>SO8</i>
Silicon process technology	<i>BIPOLAR</i>

Locations	
Wafer fab location	<i>ANG MO KIO 6"</i>
Assembly plant location	<i>BOUSKOURA (Morocco)</i>
Reliability assessment	<i>Pass</i>

General Information	
Product Line	<i>U093</i>
Product division	<i>I&PC</i>
Package	<i>SO8</i>
Silicon process technology	<i>BCD1</i>

Locations	
Wafer fab location	<i>ANG MO KIO 6"</i>
Assembly plant location	<i>BOUSKOURA (Morocco)</i>
Reliability assessment	<i>Pass</i>

DOCUMENT HISTORY

Version	Date	Pages	Author	Comment
1.0	23-Jan-14	9	S. Regini	Original document

Issued by
Samantha Regini

Approved by
Antonino Motta

TABLE OF CONTENTS

1 <i>Applicable and Reference Documents</i>	3
2 <i>Reliability Evaluation Overview</i>	4
2.1 Objectives	4
2.2 Conclusion	4
3 <i>Device Characteristics</i>	5
3.1 Traceability	5
3.1.1 TV1 – UE27BD6.....	5
3.1.2 TV2 – 0303AC6.....	6
3.1.2 TV3 – U093ACZ.....	6
4 <i>Tests results summary</i>	7
4.1 Test plan and results summary	7
3.1.1 TV1 – UE27BD6.....	7
3.1.2 TV2 – 0303AC6.....	7
3.1.2 TV3 – U093ACZ.....	8
5 <i>Tests Description & Detailed Results</i>	9
5.1 Package oriented tests	9
5.1.1 Pre-Conditioning.....	9
5.1.2 High Temperature Storage	9
5.1.3 Thermal Cycles	9
5.1.4 Autoclave.....	9
5.1.6 Temperature Humidity Bias.....	9

1 APPLICABLE AND REFERENCE DOCUMENTS

Document reference	Short description
AEC-Q100	: Stress test qualification for integrated circuits
8161393	: General Specification For Product Development

2 RELIABILITY EVALUATION OVERVIEW

2.1 Objectives

This report contains all the reliability activities in order to evaluate the new HD lead frame (320 units/strip vs 120 units/strip) used for the assembly of SO8 package in BOUSKOURA (Morocco) assy plant. With respect the current pre-plated lead frame, the new HD LF is a Cu - Ag spot lead frame; a pure tin lead plating process step will be introduced in the process flow after post mold curing step and before cropping.

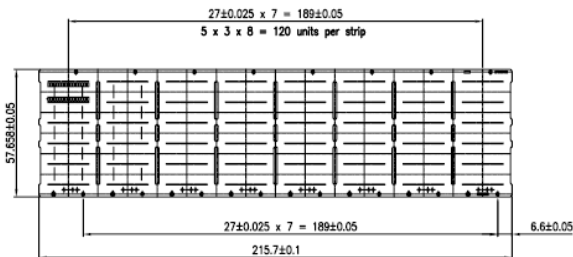


Fig1: Current SO8 LF (5x3x8=120 units /strip; 57.7x215.7 mm)

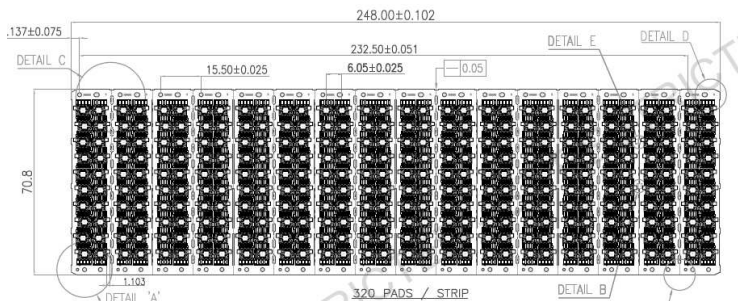


Fig2: New HD SO8 LF (10x2x16=320 units /strip; 70.8x248 mm)

In addition a new resin halogen free SUMITOMO G630AY will be introduced to substitute the current SUMITOMO G700K resin.

The reliability evaluations have been performed 3 test vehicles: UE27BD6, 0303AC6 and U093ADZ devices diffused in AMK6" and assembled in SO8 package in Bouskoura.

According to Reliability Qualification Plan, below is the list of the trials performed:

Package Oriented Tests

- Preconditioning
- Temperature Cycling
- Autoclave
- High Temperature Storage Life
- Temperature Humidity Bias

2.2 Conclusion

Taking in account the **results of the trials performed** the new HD LF and the new resin halogen free SUMITOMO G630AY used in SO8 package assembled in BOUSKOURA (Morocco) ASSY PLANT **can be qualified** from reliability viewpoint.

3 DEVICE CHARACTERISTICS

3.1 Traceability

3.1.1 TV1 - UE27BD6

Wafer fab information	
Wafer fab manufacturing location	ANG MO KIO
Wafer diameter	6"
Wafer thickness	375 μ m
Silicon process technology	BCD2S
Die finishing back side	CHROMIUM / NIKEL/ GOLD
Die size	1790 *1870 μ m
Bond pad metallization layers	AlSiCu
Passivation	SiN/POLYIMIDE
Metal levels	2

Assembly Information	
Assembly plant location	BOUSKOURA (Morocco)
Package description	SO 8
Die pad size	94 x125 mils
Frame material	SO 8L 94x125 HD OpA 320u SpAg - Sumitomo
Molding compound	SUMITOMO EME-G630AY
Wires bonding materials/diameters	Cu 1 mil
Die attach material	ABLEBOND 8601S-25
Lead solder material	Sn

3.1.2 TV2 - 0303AC6

Wafer fab information	
Wafer fab manufacturing location	ANG MO KIO
Wafer diameter	6"
Wafer thickness	375 μ m
Silicon process technology	BIPOLAR
Die finishing back side	RAW SILICON
Die size	1890*2120 μ m
Bond pad metallization layers	AlSiCu
Passivation	SiN
Metal levels	1

Assembly Information	
Assembly plant location	BOUSKOURA (Morocco)
Package description	SO 8
Die pad size	94 x125 mils
Frame material	SO 8L 94x125 HD OpA 320u SpAg / Supplier Sumitomo
Molding compound	SUMITOMO EME-G630AY
Wires bonding materials/diameters	Cu 1mils
Die attach material	GLUE ABLEBOND 8601S-25
Lead solder material	Sn

3.1.3 TV3 - U093ADZ

Wafer fab information	
Wafer fab manufacturing location	ANG MO KIO
Wafer diameter	6"
Wafer thickness	375 μ m
Silicon process technology	BCD1
Die finishing back side	CHROMIUM / NIKEL/ GOLD
Die size	2590,2060 μ m
Bond pad metallization layers	AlSi
Passivation	SiN
Metal levels	1

Assembly Information	
Assembly plant location	BOUSKOURA (Morocco)
Package description	SO 8
Die pad size	94 x125 mils
Frame Material	SO 8L 94x125 HD OpA 320u SpAg / Supplier Sumitomo
Molding compound	SUMITOMO EME-G630AY
Wires bonding materials/diameters	Cu 1 mil
Die attach material	ABLEBOND 8601S-25
Lead solder material	Sn

4 TESTS RESULTS SUMMARY

4.1 Test plan and results summary

4.1.1 TV1 - UE27BD6

Package Oriented Tests							
Test	Method	Conditions	Failure/SS			Duration	Note
			Lot 1	Lot 2	Lot 3		
PC	Pre-Conditioning: Moisture sensitivity level 1						
		168h 85°C/85% - 3 reflow PBT 260°C	0/154				no delamination
AC	Autoclave						
	PC before	121°C 2atm	0/77			168h	
TC	Temperature Cycling						
	PC before	Temp. range: -65/+150°C	0/77			1000cy	
HTSL	High Temperature Storage						
	No bias	Tamb=150°C	0/77			1000h	

4.1.2 TV2 - 0303AC6

Package Oriented Tests							
Test	Method	Conditions	Failure/SS			Duration	Note
			Lot 1	Lot 2	Lot 3		
PC	Pre-Conditioning: Moisture sensitivity level 1						
		168h 85°C/85% - 3 reflow PBT 260°C	0/231				No delamination
AC	Autoclave						
	PC before	121°C 2atm	0/77			96h	
TC	Temperature Cycling						
	PC before	Temp. range: -65/+150°C	0/77			1000cy	
HTSL	High Temperature Storage						
	No bias	Tamb=150°C	0/77			1000h	
THB	Temperature Humidity Bias						
	PC before	Ta=85°C, 85%R.H, Vcc=+25V	0/77			1000h	

4.1.3 TV3 - U093ADZ

Package Oriented Tests							
Test	Method	Conditions	Failure/SS			Duration	Note
			Lot 1	Lot 2	Lot 3		
PC	Pre-Conditioning: Moisture sensitivity level 1						
		168h 85°C/85% - 3 reflow PBT 260°C	0/154				No delamination
AC	Autoclave						
	PC before	121°C 2atm	0/77			168h	
TC	Temperature Cycling						
	PC before	Temp. range: -65/+150°C	0/77			1000cy	
HTSL	High Temperature Storage						
	No bias	Tamb=150°C	0/77			1000h	

5 TESTS DESCRIPTION & DETAILED RESULTS

5.1 Package oriented tests

5.1.1 Pre-Conditioning

The device is submitted to a typical temperature profile used for surface mounting, after a controlled moisture absorption.

The scope is to verify that the surface mounting stress does not impact on the subsequent reliability performance. The typical failure modes are "pop corn" effect and delamination.

5.1.2 High Temperature Storage

The device is stored in unbiased condition at the max. temperature allowed by the package materials, sometimes higher than the max. operative temperature.

The scope is to investigate the failure mechanisms activated by high temperature, typically wire-bonds solder joint ageing, data retention faults, metal stress-voiding

5.1.3 Thermal Cycles

The purpose of this test is to evaluate the thermo mechanical behavior under moderate thermal gradient stress.

Test flow chart is the following:

- Initial testing @ Ta=25°C.
- Readout @ 500 cycles.
- Final Testing @ 1000 cycles @ Ta=25°C.

TEST CONDITIONS:

- Ta= -50°C to +150°C(air)
- 15 min. at temperature extremes
- 1 min. transfer time

5.1.4 Autoclave

The purpose of this test is to point out critical water entry path with consequent corrosion phenomena related to chemical contamination and package hermeticity.

Test flow chart is the following:

- Initial testing @ Ta=25°C.
- Final Testing (168hrs) @ Ta=25°C.

TEST CONDITIONS:

- P=2.08 atm
- Ta=121°C
- test time= 168 hrs

5.1.5 Temperature Humidity Bias

The test is addressed to put in evidence problems of the die-package compatibility related to phenomena activated in wet conditions such as electro-chemical corrosion.

The device is stressed in static configuration approaching some field status like power down. Temperature, Humidity and Bias are applied to the device in the following environmental conditions => Ta=85°C / RH=85%.

Input pins to Low / High Voltage (alternate) to maximize voltage contrast.

Test Duration 1000 h.

The flow chart is the following:

- Initial testing @ Ta=25°C, 85°C
- Check @ 168 and 500hrs
- Final Testing (1000 hr.) @ Ta=25°C, 85°

Please Read Carefully:

Information in this document is provided solely in connection with ST products. STMicroelectronics NV and its subsidiaries ("ST") reserve the right to make changes, corrections, modifications or improvements, to this document, and the products and services described herein at any time, without notice.

All ST products are sold pursuant to ST's terms and conditions of sale.

Purchasers are solely responsible for the choice, selection and use of the ST products and services described herein, and ST assumes no liability whatsoever relating to the choice, selection or use of the ST products and services described herein.

No license, express or implied, by estoppel or otherwise, to any intellectual property rights is granted under this document. If any part of this document refers to any third party products or services it shall not be deemed a license grant by ST for the use of such third party products or services, or any intellectual property contained therein or considered as a warranty covering the use in any manner whatsoever of such third party products or services or any intellectual property contained therein.

UNLESS OTHERWISE SET FORTH IN ST'S TERMS AND CONDITIONS OF SALE ST DISCLAIMS ANY EXPRESS OR IMPLIED WARRANTY WITH RESPECT TO THE USE AND/OR SALE OF ST PRODUCTS INCLUDING WITHOUT LIMITATION IMPLIED WARRANTIES OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE (AND THEIR EQUIVALENTS UNDER THE LAWS OF ANY JURISDICTION), OR INFRINGEMENT OF ANY PATENT, COPYRIGHT OR OTHER INTELLECTUAL PROPERTY RIGHT.

ST PRODUCTS ARE NOT DESIGNED OR AUTHORIZED FOR USE IN: (A) SAFETY CRITICAL APPLICATIONS SUCH AS LIFE SUPPORTING, ACTIVE IMPLANTED DEVICES OR SYSTEMS WITH PRODUCT FUNCTIONAL SAFETY REQUIREMENTS; (B) AERONAUTIC APPLICATIONS; (C) AUTOMOTIVE APPLICATIONS OR ENVIRONMENTS, AND/OR (D) AEROSPACE APPLICATIONS OR ENVIRONMENTS. WHERE ST PRODUCTS ARE NOT DESIGNED FOR SUCH USE, THE PURCHASER SHALL USE PRODUCTS AT PURCHASER'S SOLE RISK, EVEN IF ST HAS BEEN INFORMED IN WRITING OF SUCH USAGE, UNLESS A PRODUCT IS EXPRESSLY DESIGNATED BY ST AS BEING INTENDED FOR "AUTOMOTIVE, AUTOMOTIVE SAFETY OR MEDICAL" INDUSTRY DOMAINS ACCORDING TO ST PRODUCT DESIGN SPECIFICATIONS. PRODUCTS FORMALLY ESCC, QML OR JAN QUALIFIED ARE DEEMED SUITABLE FOR USE IN AEROSPACE BY THE CORRESPONDING GOVERNMENTAL AGENCY.

RESTRICTIONS OF USE AND CONFIDENTIALITY OBLIGATIONS:

THIS DOCUMENT AND ITS ANNEXES CONTAIN ST PROPRIETARY AND CONFIDENTIAL INFORMATION. THE DISCLOSURE, DISTRIBUTION, PUBLICATION OF WHATSOEVER NATURE OR USE FOR ANY OTHER PURPOSE THAN PROVIDED IN THIS DOCUMENT OF ANY INFORMATION CONTAINED IN THIS DOCUMENT AND ITS ANNEXES IS SUBMITTED TO ST PRIOR EXPRESS AUTHORIZATION. ANY UNAUTHORIZED REVIEW, USE, DISCLOSURE OR DISTRIBUTION OF SUCH INFORMATION IS EXPRESSLY PROHIBITED.

Resale of ST products with provisions different from the statements and/or technical features set forth in this document shall immediately void any warranty granted by ST for the ST product or service described herein and shall not create or extend in any manner whatsoever, any liability of ST.

ST and the ST logo are trademarks or registered trademarks of ST in various countries.

Information in this document supersedes and replaces all information previously supplied.

The ST logo is a registered trademark of STMicroelectronics. All other names are the property of their respective owners

© 2014 STMicroelectronics - All rights reserved.

STMicroelectronics group of companies

Australia - Belgium - Brazil - Canada - China - Czech Republic - Finland - France - Germany - Hong Kong - India - Israel - Italy - Japan -
Malaysia - Malta - Morocco - Philippines - Singapore - Spain - Sweden - Switzerland - United Kingdom - United States of America

www.st.com

